

THICKNESS OSCILLATION EFFECT IN PHOTOEXPANSION AND PHOTOCONTRACTION OF AMORPHOUS SELENIUM

M. POPESCU*, F. SAVA, A. VELEA, I-D. SIMANDAN, K. SHIMAKAWA^a
National Institute R&D of Materials Physics, Bucharest-Magurele, Romania
^aGifu University, Gifu, Japan

The chalcogenide glasses and thin films are characterized by specific optical phenomena (photodarkening, photobleaching) and mechanical ones (photocontraction, photoexpansion) [1, 2]. The modifications of the properties are basically due to special layer structure of such materials [3]. The photo-induced expansion of amorphous selenium films was measured in situ for the first time using optoelectronic interference enhanced by image processing [4] (Fig. 1).

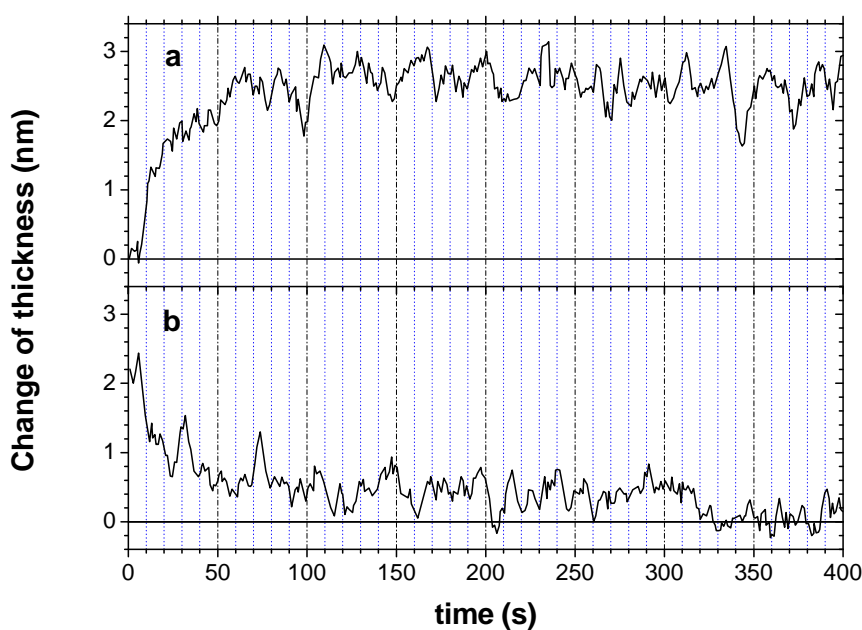


Fig. 1 Measured photoinduced changes in amorphous selenium. Upper panel: expansion due to illumination (a). Lower panel: shrinkage after switching off illumination (b).

We have processed the fundamental oscillation covered by strong noise occurring on the curve.

In order to demonstrate that a significant oscillation of thickness does exist, we have tried to separate the noise from a possible regular oscillation. To this aim we performed the Fourier transformation of the strings of data presented in Fig. 2 a and b. The results can be seen in Fig. 3.

*Corresponding author: mpopescu@infim.ro; velea@infim.ro

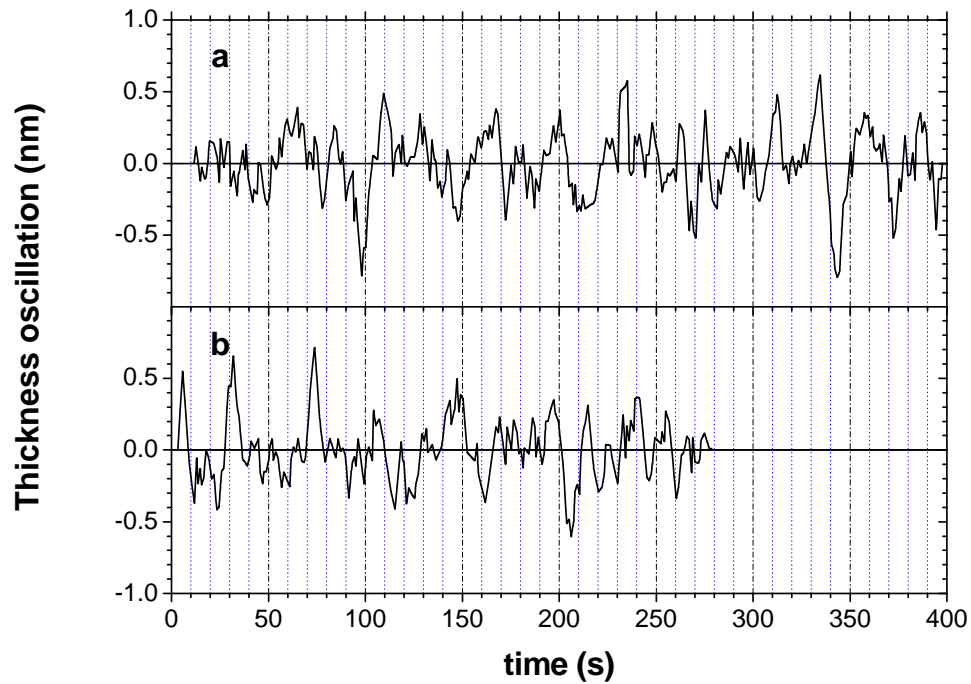


Fig. 2 The curves from figure 1 transformed by subtracting the average increase (a) and decrease (b).

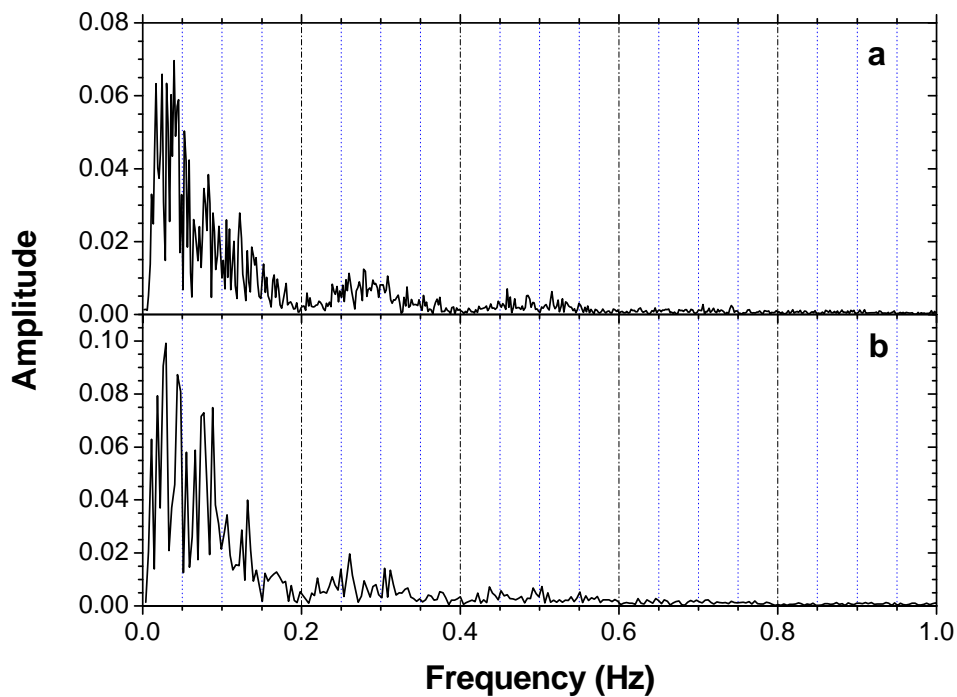


Fig. 3 Frequency spectrum for the data in figure 2.

By transforming the frequency spectrum into a period spectrum, we got period spectra that evidence oscillations of well-defined time-length situated at 41s, 59 s, 88 s (Fig. 4a) and 36 s, 54 s, 91 s (Fig. 4b).

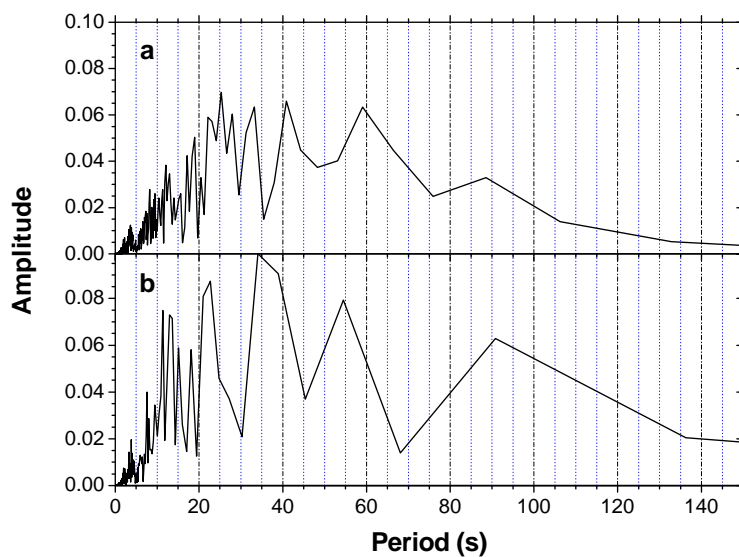


Fig. 4 The periods of the oscillations as obtained from the frequency spectrum.

In order to point out in the experimental data the existence of oscillations corresponding to the dominant period of 60 s we have applied a smoothing procedure (Savitzky-Golay method). Figure 5 shows the results.

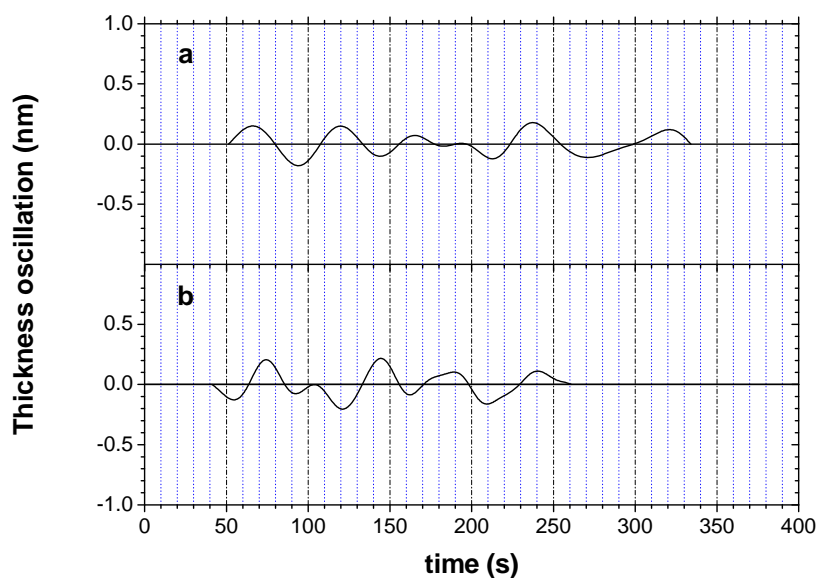


Fig. 5 The experimental data from figure 2, smoothed as to evidence the fundamental oscillations of the thickness

It is quite remarkable that both expansion and compression of the thickness of amorphous selenium film exhibit a dominant oscillation of well defined period: 60 s.

The mechanism and theory of this new phenomenon is under development.

References

- [1] M. Popescu, *Non-Crystalline Chalcogenides*, Kluwer Publishers, 2000.
- [2] Ke. Tanaka, T. Naskagawa, A. Odajima, *J. Phys. Chem. Lett. B* **54**(1) L3-L7 (1986).
- [3] Ke. Tanaka, *J. Non-Cryst. Solids* **103**, 149 (1988).
- [4] Y. Ikeda, K. Shimakawa, *J. Non-Cryst. Solids*, **338-340**, 539 (2004).